



## FRACTIONATION OF HEMICELLULOSE FROM RICE STRAW BY ALKALINE EXTRACTION AND ETHANOL PRECIPITATION

(Pemisahan Hemiselulosa daripada Hampas Batang Padi melalui Pengekstrakan Beralkali dan Pemendakan Etanol)

Nur Hazlilla Zulyadi, Sabiha Hanim Saleh\*, Siti Halimah Sarijo

*School of Chemistry and Environment, Faculty of Applied Sciences,  
Universiti Teknologi MARA (UiTM), 40450 Shah Alam, Selangor, Malaysia*

*\*Corresponding author: sabihahanim@salam.uitm.edu.my*

Received: 24 February 2015; Accepted: 27 October 2015

### Abstract

Hemicelluloses were extracted from rice straw using alkaline extraction and ethanol precipitation. The effects of different extraction conditions; temperature (45 – 65 °C), pH (4.5 – 6.5), and concentrations of NaOH (0.25 – 1 M) on the hemicellulose yield were investigated. Two hemicellulosic fractions namely Ha<sub>1</sub> and Ha<sub>2</sub> were obtained by precipitation of alkaline soluble hemicellulose in 0.2 volumes and 4 volumes ethanol, respectively. The Ha<sub>1</sub> and Ha<sub>2</sub> were further characterized to obtain total sugar, monosaccharides and Klason Lignin content. The highest hemicellulose yield for Ha<sub>1</sub> was 4.00 % obtained at 55 °C and pH 5.5 with 0.25 M of NaOH, whereas the highest hemicellulose yield for Ha<sub>2</sub> was 19.88 % obtained at 55 °C and pH 5.5 with 0.5 M of NaOH. This study revealed that hemicellulose yield is dependent on the pH, temperature and concentration of NaOH in the alkaline extraction.

**Keywords:** hemicelluloses, rice straw, alkaline extraction, ethanol precipitation

### Abstrak

Hemiselulosa daripada hampas batang padi telah diekstrak melalui pengekstrakan beralkali dan pemendakan etanol. Kesan perbezaan kondisi pengekstrakan; suhu (45 – 65 °C), pH (4.5 – 6.5), dan kepekatan NaOH (0.25 – 1 M) ke atas hasil hemiselulosa dikaji. Dua pecahan hemiselulosa, Ha<sub>1</sub> and Ha<sub>2</sub> telah diperolehi melalui pemendakan hemiselulosa larut alkali dalam isipadu etanol 0.2 dan 4 masing-masing. Ha<sub>1</sub> and Ha<sub>2</sub> dicirikan oleh jumlah gula, kandungan monosakarida dan Klason Lignin. Hasil hemiselulosa tertinggi untuk Ha<sub>1</sub> adalah 4.00 % yang diperolehi pada suhu 55 °C, pH 5.5 and 0.25 M NaOH, manakala untuk Ha<sub>2</sub> adalah 19.88 % diperolehi pada suhu 55 °C, pH 5.5 and kepekatan 0.5 M NaOH. Kajian ini membuktikan hasil hemiselulosa bergantung kepada pH, suhu dan kepekatan NaOH dalam pengekstrakan beralkali.

**Kata kunci:** hemiselulosa, hampas batang padi, pengekstrakan beralkali, pemendakan etanol

### Introduction

The main cereal crop in the whole wide world is rice, which is being produced in more than 148 million hectares with huge range of ecosystem. The scientific name of paddy is *Oryza sativa*. It is an important cereal crop that produce a lot of residues which is rice straw [1]. Rice straw is the rice plant stalk that is left as waste product on the field after harvesting of the rice grain [2]. A lot of rice straw are disposed by biomass burning that leads to air pollution. Therefore, a lot of research work has been performed to find ways of utilizing these agricultural waste. Hemicellulose is the second most abundant polysaccharide in nature, representing approximately 20-30% of

lignocellulosic biomass [3]. Hemicellulose polymers are complex components in the plants cell wall. With cellulose and lignin, hemicellulose form hydrogen bonds and covalent bond respectively.

The hemicelluloses are used in various industrial applications such as food additives, biodegradable films and in medicinal applications [4]. Various methods were used to isolate hemicellulose from the agricultural waste. Among these methods, alkaline extraction is most widely used. Alkaline solution hydrolyzes the ester linkage between hemicellulose and other components, resulted in isolating hemicellulose in the aqueous media. Usually the isolation of hemicellulose is done by using alkaline solution such as NaOH for softwood and KOH for hardwood [5]. The aim of this study was to optimize the alkaline extraction conditions and ethanol precipitation of hemicelluloses from rice straw. The effects of the concentration of NaOH, temperature and pH on hemicellulose percentage yield were investigated.

## Materials and Methods

### Materials

Rice straw was obtained from local sources (Perlis, Malaysia). It was dried and cut into small pieces. The straw was ground to pass a 0.08 mm size screen and stored at room temperature. All other chemicals used were of analytical grade unless otherwise stated.

### Extraction of hemicelluloses

Extraction of hemicellulose was carried out by mixing the rice straw with 0.25 M sodium hydroxide (NaOH) with ratio of 1:25 (w/v). The mixture was stirred at 400 rpm and heated at constant temperature of 55 °C for 2 hours. After filtration, the pH of the solution was adjusted to pH 5.5 by adding 6 M hydrochloric acid (HCl). Then the mixtures were kept at 4.0 °C for 24 hours. The mixture was then centrifuged at 3500 rpm for 15 minutes. Ethanol 0.2 volumes and 4 volumes containing 10 % of acetic acid were added to the liquid fraction to precipitate Ha<sub>1</sub> and Ha<sub>2</sub> respectively. Both hemicellulose fractions (Ha<sub>1</sub> and Ha<sub>2</sub>) were obtained and dried at 40.0 °C for 24 hours. In order to optimize the alkaline extraction conditions, the extraction was carried out at various concentration of NaOH (0.25 M, 0.5 M and 1 M) temperature (45 °C, 55 °C, and 65 °C) and pH (4.5, 5.5 and 6.5).

### Analytical method

Total sugar content was measured according to phenol-sulphuric acid method [6]. The hemicellulose fraction with unknown concentration was added with 0.5 mL of 5.0 % phenol solution and the mixture was shaken. A volume of 2.5 mL concentrated H<sub>2</sub>SO<sub>4</sub> was quickly added to the mixture (phenol-hemicellulose) and shaken once again. These solutions were then analysed where the absorbance of the mixtures were recorded at 480 nm using UV-Visible spectrophotometer. The hemicelluloses yield (%) was calculated based on total sugar content in the hemicelluloses fraction. The monosaccharides sugar was determined by using a high performance liquid chromatography (HPLC) (Agilent Technologies 1200 Series, Germany) using Aminex HPX 87P column (300 mm x 7.8 mm). The HPLC was equipped with a refractive index detector (G 1362A, Agilent Technologies 1200 Series, Germany) and column oven (Agilent Technologies 1200 Series, Germany). The hemicellulose fraction was filtered through a 0.20 µm nylon syringe filter (Minisart, Sartorius AG, Germany) prior directly injected to the HPLC system. The hemicellulose fractions were eluted using deionised water as the mobile phase at column temperature of 80 °C and a flow rate of 0.5 mL/min. Klason lignin content was determined following TAPPI method T222. The FTIR spectra of the hemicellulose fractions were obtained on a FT-IR spectroscopy (Nicolet 500) using a KBr disc containing 1% finely ground samples. Spectra were recorded between 4000 and 400 cm<sup>-1</sup> at a resolution of 4 cm<sup>-1</sup>.

### Statistical analysis

ANOVA was used to analyse the data of experiment and Duncan's multiple range test was applied in order to determine the significant difference (P<0.05) of samples using Statistical Package for Social Science, Version 10 (SPSS Inc., Illinois). The result was expressed as mean ± SD (standard deviation).

## Results and Discussion

### Effect of NaOH concentration

Alkaline extraction was carried out to investigate the effects of NaOH concentrations; 0.25 M, 0.5 M and 1 M on hemicellulose yield, while other parameters were fixed as followed : pH 5.5 and temperature 55 °C. As shown in


Figure 1 (a), hemicellulose yield for both Ha<sub>1</sub> and Ha<sub>2</sub> increased as NaOH concentration increased from 0.25 M to 0.5 M but then decreased tremendously when the NaOH concentration was increased to 1 M. This indicates that hemicellulose extraction was best performed at mild conditions. Hemicellulose yield for both, Ha<sub>1</sub> and Ha<sub>2</sub> were highest at 0.5 M NaOH concentration. Statistical analysis for Ha<sub>1</sub> showed that there were no significant differences between 0.25 M NaOH and 0.5 M NaOH ( $P > 0.05$ ), while there were significant differences among 0.25 M NaOH and 1 M NaOH. Thus 0.25 M NaOH concentration was chosen for further analysis for Ha<sub>1</sub>. On the other hand, the statistical analysis for Ha<sub>2</sub> showed that there were significant differences between 0.25 M, 0.5 M and 1 M NaOH ( $P < 0.05$ ). Therefore, 0.5 M NaOH concentration was chosen for further analysis for Ha<sub>2</sub>.

### Effect of temperature

The effects of different temperatures (45 – 65 °C) on the yield of hemicellulosic fractions; Ha<sub>1</sub> and Ha<sub>2</sub> were studied while the other parameters were fixed; pH 5.5 with 0.25 M NaOH for Ha<sub>1</sub> and pH 5.5 with 0.5 M NaOH for Ha<sub>2</sub>. Statistical analysis of hemicellulose yield, Ha<sub>1</sub> and Ha<sub>2</sub> showed that the significant difference existence between temperature of 45 °C and 55 °C and among hemicellulose extracted at 55 °C and 65 °C ( $P < 0.05$ ), however there is no significant difference between hemicellulose yield extracted at 45 °C and 65 °C ( $P > 0.05$ ). Based on Figure 1 (b), the best temperature for alkaline extraction was at 55°C which gave the highest hemicellulose yield. The presence of high lignin content hindered the yield of hemicellulose in Ha<sub>1</sub> resulted in lower hemicellulose yield than Ha<sub>2</sub>. The hemicellulose yield for both Ha<sub>1</sub> and Ha<sub>2</sub> significantly increased from 45 °C to 55 °C and as temperature of extraction reached 65 °C, the yield of hemicelluloses significantly decreased. The yield of hemicellulose decreased at 65 °C due to less degradation of macromolecular hemicellulose. The minor degradation occurred mainly because of the linkages between glycosyl units were cleaved at high temperature [6].

### Effect of pH

pH was another factor which affected the efficiency of hemicellulose extraction. The effect of pH for hemicellulosic fractions, Ha<sub>1</sub> and Ha<sub>2</sub> were studied at different pH (4.5 – 6.5) while the other parameters were fixed; 0.25 M NaOH and temperature of 55 °C for Ha<sub>1</sub> while 0.5 M NaOH and temperature of 55 °C for Ha<sub>2</sub>. Statistical analysis for Ha<sub>1</sub> and Ha<sub>2</sub> showed that the significant difference existence between pH of 4.5 and 5.5 and between pH 5.5 and 6.5, ( $P < 0.05$ ), however there is no significant difference between pH 4.5 and 6.5 ( $P > 0.05$ ). There was an increasing trend in hemicellulose yield from pH 4.5 to 5.5 and decreasing trend from pH 5.5 to 6.5 for both Ha<sub>1</sub> and Ha<sub>2</sub>. This indicated that minor degradation occurred when the pH was slightly acidic (pH 4.5) and at neutral condition (pH 6.5). Figure 1 (c) showed that the suitable pH to yield the maximum concentration for both Ha<sub>1</sub> and Ha<sub>2</sub> was at pH 5.5. Thus, pH 5.5 was favorable to isolate hemicellulose from rice straw using alkaline extraction.

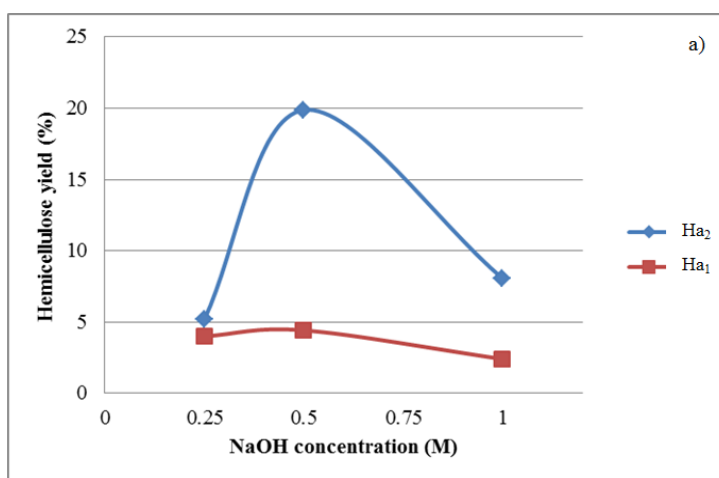

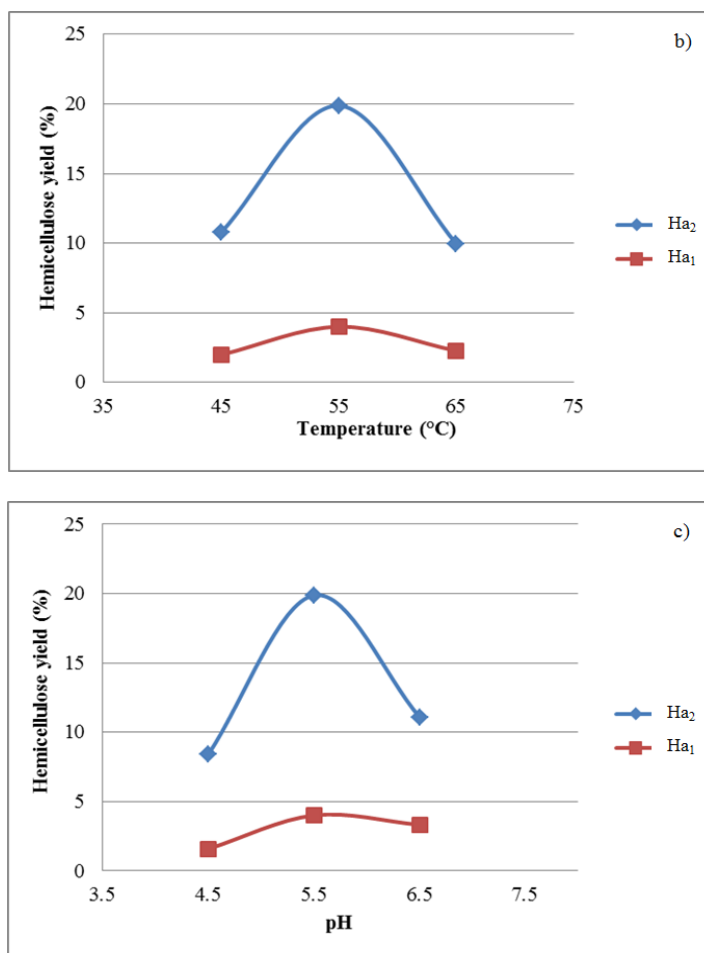


Figure 1. Effects of NaOH concentration (a), temperature (b), and pH (c) on hemicellulose yield (%) Ha<sub>1</sub> and Ha<sub>2</sub>.

### Klason Lignin content

The Klason lignin content for both hemicellulose fractions, Ha<sub>1</sub> and Ha<sub>2</sub> is shown in Table 1. The result showed that Ha<sub>1</sub> contain more lignin (11.72 %) than Ha<sub>2</sub> (4.22 %). Table 1 showed that as the volume of ethanol decreased (0.2 v) in Ha<sub>1</sub>, the Klason lignin content increased and as the volume of ethanol increased (4v) in Ha<sub>2</sub>, the Klason lignin content decreased. The increased volume of ethanol (4v) increased the polarity of plant cell wall in Ha<sub>2</sub> exposed it more to the solvent thus promote the lignin removal [7].

Table 1. Monosaccharide composition and Klason Lignin content for Ha<sub>1</sub> and Ha<sub>2</sub>

	Glucose (mg/mL)	Arabinose (mg/mL)	Xylose (mg/mL)	Ara/Xyl ratio	Klason Lignin (%)
Ha <sub>1</sub>	0.57 ± 0.44	0.10 ± 0.02	0.27 ± 0.02	0.36	11.72 ± 5.07
Ha <sub>2</sub>	0.70 ± 0.18	0.96 ± 0.07	0.05 ± 0.05	21.08	4.22 ± 1.32

Data means and standard deviation n=3. Ha<sub>1</sub> represent hemicellulose high lignin prepared by alkaline extraction from rice straw with 0.2v ethanol precipitation. Ha<sub>2</sub> represent hemicellulose low lignin prepared by alkaline extraction from rice straw with 0.4v ethanol precipitation.

### Monosaccharide analysis by HPLC

As shown in Table 1, both Ha<sub>1</sub> and Ha<sub>2</sub> composed of glucose, arabinose and xylose. The predominant sugar component for Ha<sub>1</sub> was glucose while for Ha<sub>2</sub> was arabinose. Ha<sub>2</sub> consisted of higher glucose concentration mainly because the presence of glucans which associated with xylans in primary cell wall, which were less associated with lignin. The xylose concentration higher in Ha<sub>1</sub> as compared to Ha<sub>2</sub>. The lower amount of arabinose in Ha<sub>1</sub> suggested that the hemicellulose was closely associated to the cellulose surface [8]. Hemicellulose fraction, Ha<sub>2</sub> contained higher amount of Ara/Xyl (21.08) whereas Ha<sub>1</sub> showed lower Ara/Xyl ratio (0.36). Higher amount of Ara/Xyl means that the hemicellulose obtained more linear arabinoxylan while lower Ara/Xyl ratio consisted of branched arabinoxylan [9].

### FTIR Spectra

Figure 2 shows the FTIR spectra of hemicellulosic fractions (Ha<sub>1</sub>, Ha<sub>2</sub>) and rice straw within the region of 500 – 4000 cm<sup>-1</sup> including region 850 – 1200 cm<sup>-1</sup> which is typical region for hemicellulose [10]. Both hemicellulose fractions show similar features. All of the spectra showed similarity as they all have hemicellulose band (850 – 1200 cm<sup>-1</sup>), which concluded that the alkaline extraction did not change the macromolecular structure of hemicellulose. Absorption band at 1610 cm<sup>-1</sup> corresponded to the water bending mode presence for only Ha<sub>1</sub> and Ha<sub>2</sub> since hemicellulose have strong affinity towards water whereas, this band could not found in rice straw due to the presence of cellulose which hindered the water affinity [11]. Low intensity absorption band at region 850 – 1200 cm<sup>-1</sup> in Ha<sub>1</sub> compared to Ha<sub>2</sub> shows low purity of hemicellulose fraction due to the higher lignin content for Ha<sub>1</sub> compared to Ha<sub>2</sub>. The absorption band at region between 1126 – 1032 cm<sup>-1</sup> is a typical band for lignin [12]. Higher intensity absorption band at region 1126 – 1032 cm<sup>-1</sup> in Ha<sub>1</sub> compared to Ha<sub>2</sub>, proved that lignin content was higher in Ha<sub>1</sub>. The presence of absorption band at 1710 cm<sup>-1</sup> in Ha<sub>1</sub> is due to the carboxyl groups as the hydroxyl groups in lignin undergo oxidation [13]. Absorption band at 3049 cm<sup>-1</sup> is assigned to the C-H in an aromatic vibration as hemicellulose contained a small amount of lignin [10]. Absorption band at 1043 cm<sup>-1</sup> is due to the C-O-C stretching glycosidic linkages in xylans. And the absorption band at 1740 cm<sup>-1</sup> refer to acetyl carbonyl. As shown in Figure 2, broad absorption band at 3400 and 2400 cm<sup>-1</sup> is due to the stretching vibrations of OH and CH respectively and absorption band at 1200 cm<sup>-1</sup> refer to the stretching vibrations of C-O. The C-H bending vibration shows absorption bands at 1467 and 1427 cm<sup>-1</sup> while the OH bending vibration shows absorption bands at 1340 cm<sup>-1</sup> [14].

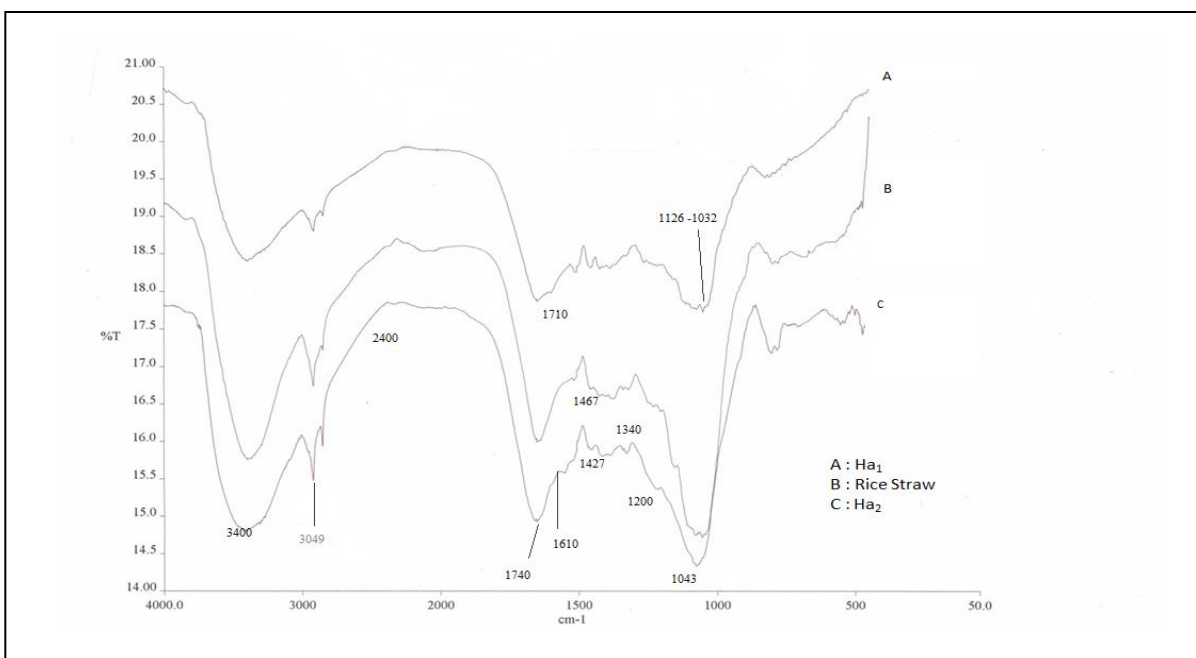


Figure 2. FTIR spectra of Ha<sub>1</sub>, Ha<sub>2</sub> and rice straw

### Conclusion

This study showed that the maximum hemicellulose percentage yield was obtained by alkaline extraction. The highest hemicellulose yield for Ha<sub>1</sub> was 4.00 % obtained at 55 °C and pH 5.5 with 0.25 M NaOH, whereas the highest hemicellulose percentage yield for Ha<sub>2</sub> was 19.88 % obtained at 55 °C and pH 5.5 with 0.5 M of NaOH. Hemicellulose yield Ha<sub>2</sub> was found to be higher than Ha<sub>1</sub>, showing that lignin content affected the percentage yield of hemicellulose.

### Acknowledgement

The authors are grateful to the Universiti Teknologi MARA, Malaysia for the financial support of this research by ZAMALAH Sokongan Pasca Siswazah (Postgraduate Supporting Fellowship), 600-RMI/DANA 5/3/PSF (18/2015), and Faculty of Pharmacy, University Teknologi Mara, Puncak Alam for HPLC facilities.

### References

1. Sharma, R. K. and Arora, D. S. (2010). Biodegradation of paddy straw obtained from different geographic locations by means of *Phlebia* spp. for animal feed. *Biodegradation*, 22: 143 – 152.
2. Lim, J. S., Abdul Manan, Z., Wan Alwi, S. R. and Hashim, H. (2012). A review on utilisation of biomass from rice industry as a source of renewable energy. *Renewable and Sustainable Energy Reviews*, 16(5): 3084 – 3094.
3. Ebringerová, A., Hromádková, Z., Híbalová, V., Xu, C., Holmbom, B., Sundberg, A., and Willför, S. (2007). Norway spruce galactoglucomannans exhibiting immunomodulating and radical-scavenging activities. *International Journal of Biology Macromolecule*, 42: 1 – 5.
4. Sabiha-Hanim, S. and Siti-Norsafurah, A. M. (2012). Physical properties of hemicellulose films from sugarcane bagasse. *Procedia Engineering*, 42: 1390 – 1395.
5. Peng, P., Peng, F., Bian, J., Xu, F., Sun, R.-C. and Kennedy, J. F. (2011). Isolation and structural characterization of hemicelluloses from the bamboo species *Phyllostachys incarnata* Wen. *Carbohydrate Polymers*, 86(2): 883 – 890.
6. Bian, J., Peng, F., Peng, X.-P., Xu, F., Sun, R.-C. and Kennedy, J. F. (2012). Isolation of hemicelluloses from sugarcane bagasse at different temperatures: Structure and properties. *Carbohydrate Polymers*, 88(2): 638 – 645.
7. Yang, D., Zhong, L.-X., Yuan, T.-Q., Peng, X.-W. and Sun, R.-C. (2013). Studies on the structural characterization of lignin, hemicelluloses and cellulose fractionated by ionic liquid followed by alkaline extraction from bamboo. *Industrial Crops and Products*, 43: 141 – 149.
8. Xiao, B., Sun, X. and Sun, R. (2001). Chemical, structural, and thermal characterizations of alkali-soluble lignins and hemicelluloses, and cellulose from maize stems, rye straw, and rice straw. *Polymer Degradation and Stability*, 74(2): 307 – 319.
9. Egiúés, I., Eceiza, A. and Labidi, J. (2013). Effect of different hemicelluloses characteristics on film forming properties. *Industrial Crops and Products*, 47: 331 – 338.
10. Rabetafika, H. N., Bchir, B., Blecker, C., Paquot, M. and Wathélet, B. (2014). Comparative study of alkaline extraction process of hemicelluloses from pear pomace. *Biomass and Bioenergy*, 61: 254 – 264.
11. Kacurakova, M., Belton, P. S., Wilson, R. H. and Hirsch, J. (1998). Hydration properties of xylan-type structure: an FTIR study of xylooligosaccharides. *Journal Science of Food and Agriculture*, 77(1): 38 – 48.
12. Cai, Y., Li, G., Nie, J., Lin, Y., Nie F. and Zhang, J. (2010). Study of the structure and biosynthetic pathway of lignin in stone cells of pear. *Science Horticulturae*, 125(3): 374 – 379.
13. Sun, R. C., Tomkinson, J., Ma, P. L. and Liang, S. F. (2000). Comparative study of hemicelluloses from rice straw by alkali and hydrogen peroxide treatments. *Carbohydrate Polymers*, 42(2): 111 – 122.
14. Kacuráková, M., Ebringerova, A., Hirsch, J. and Horomádkova, Z. (1994). Infrared study of arabinoxylans. *Journal Science of Food Agriculture*, 66 (3): 423 – 427.